

# Microstructural and creep properties of boron- and zirconium-containing cobalt-based superalloys

Peter J. Bocchini<sup>a,\*</sup>, Chantal K. Sudbrack<sup>b</sup>, Ronald D. Noebe<sup>b</sup>, David C. Dunand<sup>a,b</sup>,  
David N. Seidman<sup>a,c</sup>

<sup>a</sup> Department of Materials Science and Engineering, Northwestern University, 2220 Campus Drive, Evanston, IL 60208-3108, USA

<sup>b</sup> NASA Glenn Research Center, Materials and Structures Division, 21000 Brookpark Rd., Cleveland, OH 44135, USA

<sup>c</sup> Northwestern University Center for Atom-Probe Tomography (NUCAPT), 2220 Campus Drive, Evanston, IL 60208-3108, USA

## ARTICLE INFO

### Keywords:

Cobalt-base superalloys  
Gamma prime  
Atom-probe tomography (APT)  
Grain boundaries  
Creep

## ABSTRACT

The effects of micro-additions of boron and zirconium on grain-boundary (GB) structure and strength in polycrystalline  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) strengthened Co-9.5Al-7.5W-X at% alloys (X=0-Ternary, 0.05B, 0.01B, 0.05Zr, and 0.005B-0.05Zr at%) are studied. Creep tests performed at 850 °C demonstrate that GB strength and cohesion limit the creep resistance and ductility of the ternary B- and Zr-free alloy due to intergranular fracture. Alloys with 0.05B and 0.005B-0.05Zr both exhibit improved creep strength due to enhanced GB cohesion, compared to the baseline ternary Co-9.5Al-7.5W alloy, but alloys containing 0.01B or 0.05Zr additions display no benefit. Atom-probe tomography (APT) is utilized to measure GB segregation, where B and Zr are demonstrated to segregate at GBs. A Gibbsian interfacial excess of  $5.57 \pm 1.04$  atoms nm<sup>-2</sup> was found for B at a GB in the 0.01B alloy and  $2.88 \pm 0.81$  and  $2.40 \pm 0.84$  atoms nm<sup>-2</sup> for B and Zr, respectively, for the 0.005B-0.05Zr alloy. The GBs in the highest B-containing (0.05B) alloy exhibit micrometer-sized boride precipitates with adjacent precipitate denuded-zones (PDZs), whereas secondary precipitation at the GBs is absent in the other four alloys. The 0.05B alloy has the smallest room temperature yield strength, by 6%, which is attributed to the PDZs, but it exhibits the largest increase in creep strength (with an ~2.5 order of magnitude decrease in the minimum strain rate for a given stress at 850 °C) over the baseline Co-9.5Al-7.5W alloy.

## 1. Introduction

Cobalt-based superalloys with the  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) microstructure represent a new promising material class for alternatives to Ni-based superalloys [1–5] for high-temperature structural applications, such as jet-engine turbine disks and blades and for land-based natural gas fired turbines for producing electricity. Conventional cobalt superalloys (e.g., Haynes 188 [6]) are strengthened through solid-solution and/or carbide inclusion strengthening, rendering them useable in long-term applications at only modest temperatures, ~650 °C [2]. New cobalt superalloys based on the Co-Al-W system are, however, strengthened by  $\gamma'$ (L1<sub>2</sub>)-precipitates embedded in a  $\gamma$ (f.c.c.)-matrix similar to Ni-based superalloys [7]. The synthesis of a Co-base superalloy with the  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) microstructure has only recently been demonstrated in the Co-Al-W system [7–18], which was long thought to be unachievable based on the lack of a  $\gamma'$ (L1<sub>2</sub>) phase-field in the Co-W and Co-Al binary systems.

The creep behavior of different single-crystal [11,12,19] and

polycrystalline [16,17,20]  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) Co-based superalloys has been studied to a degree. Polycrystalline ternary Co-Al-W alloys are, however, prone to fracture at their grain boundaries (GBs) during mechanical loading [13,21]. Microalloying with B can promote the formation of GB borides, which increase GB cohesion and ductility, thereby increasing the creep strength of Co-alloys [17,20]. A consequence of the precipitating borides is the formation of large precipitate-denuded zones (PDZs). PDZs have been shown to reduce yield strength in polycrystalline Ni-base superalloys [22] and therefore minimizing the PDZ width is important for Co-alloy design. Shinagawa et al. [21] found that adding boron greatly enhances the yield strength of Co-base alloys through increased GB ductility, although in this case no GB borides were reported. GB strengthening in this situation was attributed to local segregation of B at GBs, analogous to results on polycrystalline Ni-based superalloys [23–25]. An added benefit of B is that it reduces oxidation rates in Co-superalloys by promoting the formation of a stable Al<sub>2</sub>O<sub>3</sub>-phase in the inner oxide layer at the alloy surface [26–29]. To date, B is the only GB strengthener that has been

\* Corresponding author.

E-mail address: [pbocchin@gmail.com](mailto:pbocchin@gmail.com) (P.J. Bocchini).

studied in  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) Co-based alloys, while the role of other GB strengtheners used in Ni-base superalloys, for example, Zr and C [23,25,30–32], have not yet been investigated.

In this research, different concentrations of B and Zr are studied as GB strengtheners in a ternary Co-9.5Al-7.5W alloy. Standard room temperature compression tests and Vickers microhardness measurements are utilized to determine the effects of B and Zr additions on yield strength. The effects of these GB additions on creep are evaluated employing compression creep tests at 850 °C for different constant loads. Atom-probe tomography (APT) [33,34] is utilized to measure the concentrations of the trace elements B and Zr at GBs of selected  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) Co-based superalloys [35]. Additional APT investigations are employed to measure the composition(s) of GB borides.

## 2. Experimental procedures

Five button ingots with compositions Co-9.5Al-7.5W-X at% (X=0-Ternary, 0.05B, 0.01B, 0.05Zr, and 0.005B-0.05Zr at%) weighing ~50 g each were produced by arc melting high purity Co (99.9%), Al (99.999%), B (99.5%), Zr (99.5%) and a Co-9.5Al-7.5W master alloy cast by Sophisticated Alloys Inc., under a partial pressure of argon. Ingots were remelted 3–4 times, flipping the ingot between melts to ensure that all of the constituent elements are completely incorporated into the melt. The ingots were then homogenized in a vacuum furnace at 1300 °C for 24 h followed by furnace cooling to room temperature and subsequently heated to a supersolvus temperature of 1050 °C (60 °C higher than the solvus temperature of the  $\gamma'$ (L1<sub>2</sub>)-precipitates in ternary Co-Al-W [7]) for 6 h in an Ar atmosphere and then dropped into sand and air-cooled. The final aging step was performed at 900 °C for 16 h in air and then air-cooled to obtain a  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) microstructure.

Vickers microhardness measurements were performed at ambient temperature utilizing a Struers Duramin-5 microhardness tester with an applied load of 1 kg and a dwell time of 5 s. Measurements were made across multiple grains on samples that were polished to a 1  $\mu$ m finish. Cylindrical compression samples with a 5 mm diameter and 10 mm length were cut from the aged buttons by electro-discharge machining and were used for ambient temperature compression tests and high-temperature compression creep tests. Samples for ambient temperature compression tests were sandwiched between tungsten carbide platens and deformed at a constant strain rate of 10<sup>-4</sup> s<sup>-1</sup> and deformed to 8% plastic strain with a stress accuracy equivalent to  $\pm$  15 MPa. Specimens for compression creep were sandwiched between two SiC platens lubricated with boron nitride. Compressive creep experiments were performed in air employing two dead-load creep frames, one equipped with a compressive load train and the other with a tensile load train in which a compression cage was inserted. The 0.05B and 0.01B alloys were tested using both frames to ensure compatible results, within expected experimental error. Samples used in the multi-stress creep tests were crept at 850  $\pm$  2 °C as measured by a thermocouple placed within 1 cm of the sample. Displacements were measured by an extensometer connected to a linear variable displacement transducer with a resolution of 2.5  $\mu$ m, yielding a minimum measurable strain increment of 2.5 $\times$ 10<sup>-4</sup>. Strain rates were measured using the slopes taken from the strain vs. time curves. After a steady-state strain rate was observed and maintained over a sufficiently long period of time, the stress was increased to obtain the next minimum strain rate. The tests were terminated when the strain rate was observed to increase continuously for a given stress, indicating that the sample was failing.

Scanning electron microscopy (SEM) micrographs and qualitative energy-dispersive X-ray spectroscopy (EDS) composition measurements were recorded using a Hitachi SU8030 and a Hitachi S-3400N-II SEM equipped with an Oxford INCAx-act SDD EDS detector. Samples used for SEM imaging were polished to a 1  $\mu$ m finish and

etched with a 1:1 solution of H<sub>2</sub>O<sub>2</sub>:HCl. The mean area equivalent radius ( $\langle R \rangle$ ) and the overall volume fraction ( $\phi$ ) for  $\gamma'$ -precipitates were measured by the line-intercept method [36] on SEM images taken close to a {100} plane. For an individual cuboidal  $\gamma'$ -precipitate, the circular area-equivalent radius is calculated as  $\sqrt{\frac{A}{\pi}}$ , where A is the area as determined by measuring edge-lengths of the precipitates. The grain diameter (D) was measured by averaging grain areas ( $A_g$ ) found by grain counting, and, assuming circular grains with an individual value  $D = \sqrt{\frac{4A_g}{\pi}}$ .

Nanotip specimens used for selected-area APT studies of GBs were prepared using a Ga<sup>+</sup> dual-beam focused-ion beam (FIB) microscope lift-out technique utilizing a FEI Helios Nanolab SEM/FIB. Square-topped wedges (~2  $\mu$ m<sup>2</sup>) containing a GB were extracted from the Co alloys using the FEI dual-beam FIB microscope and were then attached to either a copper transmission electron microscopy (TEM) grid or a Si micropost on a coupon, each one was subsequently sharpened to a nanotip, using Ga<sup>+</sup> ions, to an ~50 nm radius. A dual-beam FIB ion energy of 5 keV and a current of 16 pA were used for the final sharpening stage. Due to the difficulty of resolving a GB in a nanotip in the dual-beam FIB microscope, the copper grid containing the nanotips were sometimes placed directly into a JEOL JEM-2100 FasTEM to check if the GB was in an acceptable volume of the nanotip for APT analyses. The APT specimens of the solutionized alloy were prepared by cutting parallelepiped blanks (~400 $\times$ 400  $\mu$ m<sup>2</sup> cross-section). These blanks were then first electropolished with a rough-polish solution of 1:1 12.1 M concentrated hydrochloric:chromic acid, followed by a fine-polish solution of 2% perchloric acid in butoxyethanol [37,38]. APT was performed employing a Cameca 4000X-Si local-electrode atom-probe (LEAP) tomograph with a picosecond ultraviolet (wavelength =355 nm) laser at a sample temperature of 25 K, 30–50 pJ laser pulse energy, 200 kHz pulse repetition rate, and a detection rate of 0.05 ions pulse<sup>-1</sup>.

## 3. Analysis methods and results


### 3.1. Compositions and microstructure

The measured compositions of the five alloys investigated are listed in Table 1. Compositions were determined by 3-D APT analyses of the solutionized samples for which the compositions are calculated by dividing the number of atoms of species *i* by the total number of atoms in the reconstructed volume. The error is recorded as 2 $\sigma$ , where  $\sigma$  is calculated through counting statistics as  $\sqrt{C_i(1-C_i)/N_{Total}}$  [39]; where  $C_i$  is the concentration of species *i*, and  $N_{Total}$  is the total number of atoms present in the analyzed volume and 2 $\sigma$  is a measure of the

**Table 1**

Bulk compositions of the Co-9.5-7.5-X alloys measured utilizing atom-probe tomography (APT) and the mean radius,  $\langle R \rangle$ , and volume fraction,  $\phi$ , of the  $\gamma'$ (L1<sub>2</sub>)-precipitates as measured from SEM images. Parenthetical values are the 2 $\sigma$  standard deviations.

Alloy nominal composition	Alloy composition as measured by APT (at%)					$\langle R \rangle$ (nm)	$\phi$ (%)
	Co	Al	W	B	Zr		
Ternary	Bal.	9.49 (0.02)	7.45 (0.02)	–	–	37 (13)	34 (4)
0.05B	Bal.	9.56 (0.02)	7.50 (0.02)	0.0385 (0.0004)	–	35 (12)	35 (4)
0.01B	Bal.	9.85 (0.02)	7.64 (0.02)	0.0092 (0.0003)	–	36 (12)	37 (5)
0.05Zr	Bal.	9.58 (0.02)	7.40 (0.02)	–	0.0350 (0.0003)	40 (8)	37 (4)
0.005B–0.05Zr	Bal.	9.53 (0.02)	7.66 (0.02)	0.0054 (0.0005)	0.0275 (0.0010)	49 (8)	40 (5)

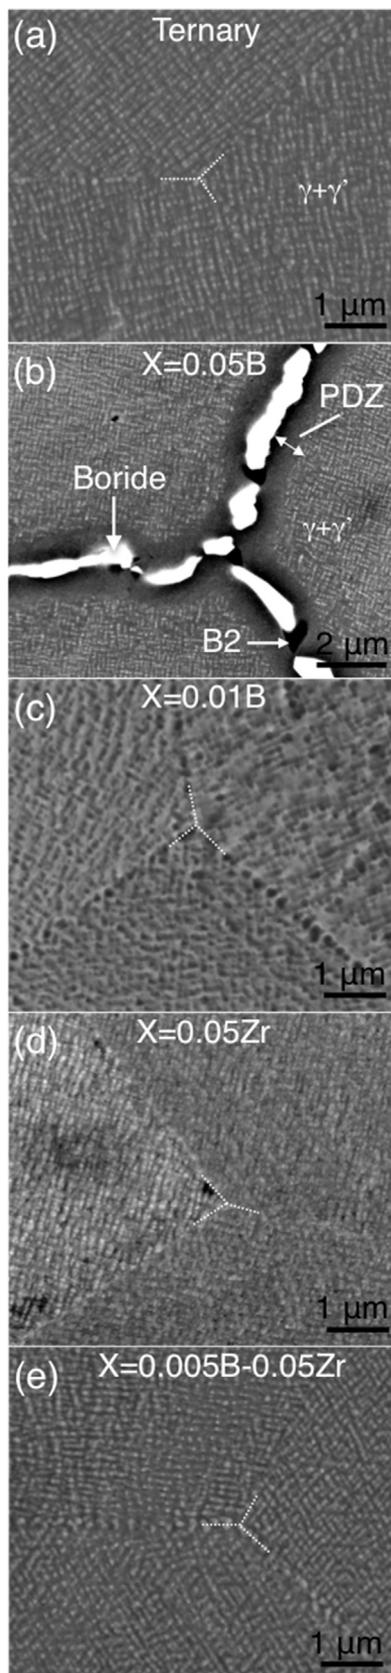

**Fig. 1.** Backscattered electron SEM micrographs of grain boundary triple points separating  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) grains in: (a) Co-9.5Al-7.5W; (b) -0.05B; (c) -0.01B; (d) -0.05Zr; and (e) -0.005B-0.05Zr at% alloys after 16 h of aging at 900 °C. Micrographs (a) and (c–e) show similar GB structures devoid of visible GB precipitates, while micrograph (b) exhibits borides (white) and CoAl(B2) (black) precipitates at the GB with adjacent precipitate denuded zones (PDZs).

scatter in the data. The compositions measured among buttons are in good agreement with the nominal target composition of Co-9.5Al-7.5W-X, where the standard deviation in the Al and W concentrations varied by 0.14 and 0.12 at%, respectively. In addition to composition, the mean  $\gamma'$ (L1<sub>2</sub>)-precipitate radius,  $\langle R \rangle$ , and the mean  $\gamma'$ (L1<sub>2</sub>)-precipitate volume fraction,  $\phi$ , are listed in Table 1. Each alloy has similar  $\langle R \rangle$  values of  $\sim 40$  nm independent of alloy composition. The mean grain diameter,  $\langle D \rangle$ , was determined to be  $\langle D \rangle = 1.5 \pm 0.5$   $\mu\text{m}$  for all alloys. The additions of B and Zr were chosen within ranges commonly found in Ni-base superalloys: 0.005–0.5 at% B and 0.01–0.05 at% Zr [20–24].

GB triple junctions are delineated with fine dashed white lines within SEM micrographs of the ternary Co-9.5Al-7.5W alloy (Fig. 1a), the two quaternary 0.01B- and -0.05Zr-alloys (Fig. 1c and d), and the quinary 0.005B-0.05Zr alloy (Fig. 1e) after aging for 16 h at 900 °C. Within the spatial resolution of the SEM, these alloys have no discernable minor phases at the GBs and consist entirely of a  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) microstructure without PDZs. In contrast, the GB triple junction in the quaternary 0.05B alloy (Fig. 1b) consists of micron-sized borides and CoAl(B2)-precipitates with a grain interior containing a  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) microstructure. This structure is similar to those of the alloys cast by Bauer et al. [17,20]. For the 0.05B alloy, the borides have an average width perpendicular to the GB of  $0.45 \pm 0.15$   $\mu\text{m}$  with a PDZ width of  $0.75 \pm 0.12$   $\mu\text{m}$  adjacent to the borides. For comparison, Bauer et al. report a 0.5  $\mu\text{m}$  boride width and 1.5  $\mu\text{m}$  PDZ for a comparable aging condition.

### 3.2. Room temperature mechanical properties of the aged alloys

Additions of B and Zr to the ternary Co-9.5Al-7.5W alloy have a negligible impact on the 0.2% yield strength at room temperature (Fig. 2a). With the exception of the 0.05B alloy, the aged alloys exhibit yield strengths that range from 594 to 618 MPa, which are statistically equivalent. The 0.05B alloy has a 6% smaller yield stress value of  $564 \pm 15$  MPa. This discrepancy may be due to the formation of PDZs in the presence of micron-sized borides at the GBs or the alloy's coarse grains, as a limited number of grain orientations are sampled in a single compression test.

Vickers microhardness, which is often used as a proxy for yield stress, was measured for all samples. The microhardness values range from 2.91 to 3.07 GPa and are within the  $2\sigma$  error of one another (Fig. 2b). Because microhardness is measured within only one grain at a time, the GB properties should not affect the results. Therefore, since B and Zr segregate at GBs, it is anticipated that the microhardness of the grain interior should be similar for all the alloys, even though the yield stress values vary somewhat among samples, which is observed in our alloys.

### 3.3. Compressive creep deformation

Compression creep experiments were performed on all alloys at 850 °C (Fig. 3). The apparent stress exponent,  $n$ , was calculated by taking the natural log of the power-law creep equation:

$$\dot{\epsilon} = A\sigma^n \exp\left(\frac{-Q}{R_g T}\right) \quad (1)$$

where  $\dot{\epsilon}$  is the secondary steady-state strain rate,  $A$  is a constant,  $\sigma$  is the applied stress,  $n$  is the apparent stress exponent,  $Q$  is the activation energy,  $R_g$  is the ideal gas constant, and  $T$  is the absolute temperature. The total time spent under stress, total strain, stress range, and stress exponent are presented in Table 2.

Creep results obtained by Bauer et al. [17] for the ternary Co-9Al-9W alloy (1 data point) and Co-9Al-9W-0.12B alloy (5 data points) are also plotted for comparison (Fig. 3). The apparent stress exponent  $n$  is labeled for each alloy and was determined using the power-law creep

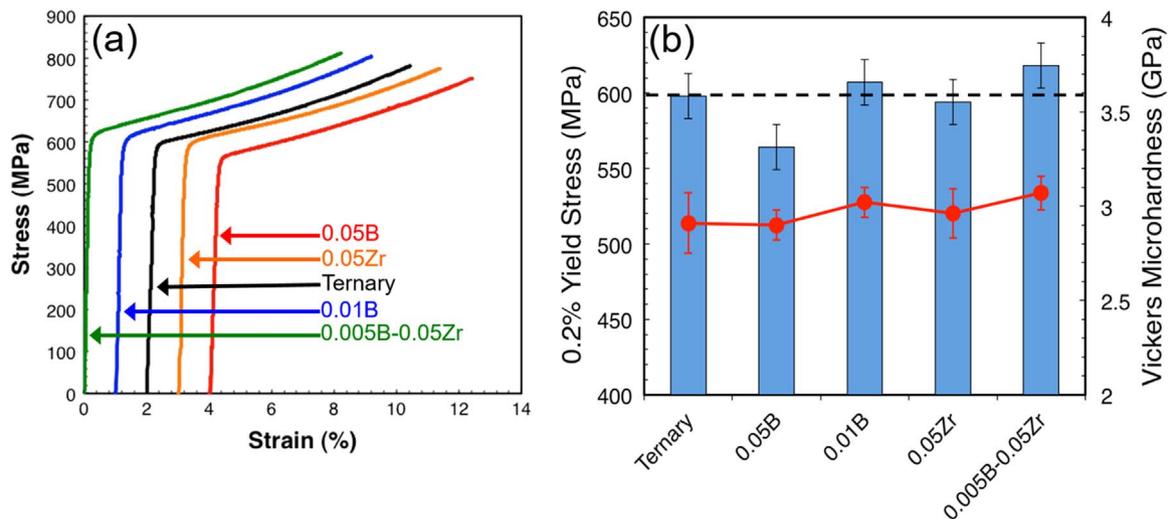


Fig. 2. (a) Stress vs. strain curves of alloys at room temperature plotted in order of descending 0.2% yield strength. (b) Plot of 0.2% yield strength shown as vertical blue bars and corresponding Vickers microhardness presented as red points.

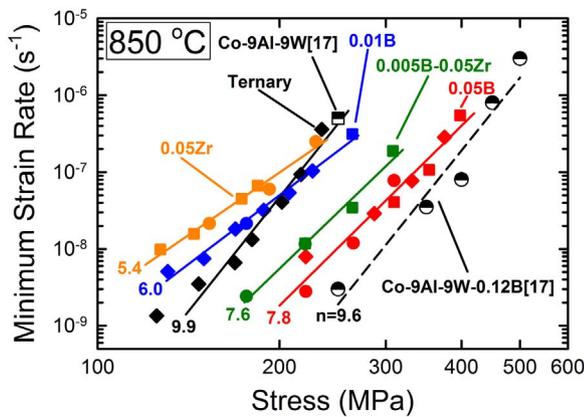


Fig. 3. Plot of minimum secondary creep rate vs. applied stress for the Co-9.5Al-7.5W, -0.05B, -0.01B, -0.05Zr, and -0.005B-0.05Zr at% alloys tested in compression at 850 °C. Alloys are identified by color and symbols representing different samples of the same alloy having different fills. The apparent stress exponent, n, of each alloy is shown at the top-left of each curve. Data from the literature for Co-9Al-9W (one single cross) and Co-9Al-9W-0.12B (multiple x) [17] are included for comparison.

Table 2

List of total creep times, total strain, and stress exponent n (with standard error in parenthesis) for all creep tests.

Alloy	Sample	Creep Time (h)	Stress Range (MPa)	Total Strain (%)	n
Ternary	1	476	105–235	3.3	9.9 (1.0)
	0.05B	1	195	221–309	2.2
0.01B	2	25	309–398	2.2	(0.6)
	3	84	221–375	1.2	
	1	121	176	2.0	6.0
0.05Zr	2	5	264	3.4	(0.3)
	3	225	130–226	2.1	
	1	101	153–230	3.6	5.4
0.005B-0.05Zr	2	248	127–184	2.6	(0.4)
	1	200	176–220	2.09	7.6
0.05B-0.005B	2	73	220–308	1.61	(0.5)


equation (Eq. (1)). In the case of the ternary Co-9.5Al-7.5W alloy, the 105 MPa data point was not used to determine the n value. This is because the secondary minimum strain rate measured at 105 and 125 MPa remained constant at  $1.5 \times 10^{-9} \text{ s}^{-1}$ , implying that the actual strain rate at 105 MPa was less than the resolution of the LVDT (linear variable differential transformer). In most cases, the strain was less

than 3.5% before the onset of failure by GB fracture as measured by a rapid increase in the strain rate. It is apparent from Fig. 3 that the additions of 0.01B or 0.05Zr do not enhance significantly the creep resistance of the ternary Co-9.5Al-7.5W alloy at higher stresses, and the quaternary alloys actually yield a higher minimum strain rates at lower stress values. The stress exponents of 6.0 and 5.4 measured for 0.01B and Co-9.5Al-7.5W-0.005B-0.05Zr alloys, respectively, are smaller than the 9.9 value measured for our ternary Co-9.5Al-7.5W alloy. The minimum strain rate of a Co-9Al-9W alloy discussed by Bauer et al., at a stress of 250 MPa, is  $\sim 5 \times 10^{-7} \text{ s}^{-1}$  [17]. For comparison, our quaternary 0.01B and 0.05Zr alloys have a minimum strain rate of  $3 \times 10^{-7} \text{ s}^{-1}$  and  $2.5 \times 10^{-7} \text{ s}^{-1}$  at applied stresses of 264 and 230 MPa, respectively, while our Co-9.5Al-7.5W alloy exhibits a strain rate of  $3.5 \times 10^{-7} \text{ s}^{-1}$  at 234 MPa. Conversely, the quinary 0.005B-0.05Zr alloy demonstrates a decrease by nearly an order of magnitude in strain rate, at all stresses, compared to the above three alloys, implying that the simultaneous addition of B and Zr has a greater effect than incorporating them individually. The 0.05B alloy, which is the only alloy containing micron-sized borides at the GBs, exhibits the best creep properties. Its minimum strain rates are greater by a factor 2–5 as compared to that of the Co-9Al-9W-0.12B alloy [17], which may be due to the smaller B and W concentrations in the former, leading to reduced boride and  $\gamma'$  volume-fractions, respectively.

### 3.4. Atom-probe tomographic analyses of grain boundary compositions in 0.01B, 0.05B, and 0.005B-0.05Zr containing alloys

#### 3.4.1. Composition of grain boundary borides

Klein et al. have hypothesized that the GB borides in Co-Al-W-B are  $W_5B_3$  [28] without measurement of their composition or crystal structure; no such measurement has been reported to our knowledge. In this research, APT was used to measure the composition across a GB boride/ CoAl(B2)-precipitate interface (Fig. 4a) extracted from the 0.05B sample. A proximity histogram [40] corresponding to an isoconcentration surface of 2 at% B across this interface displays the atomic concentrations of Co, Al, W, and B (Fig. 4b). The Al concentration decreases precipitously from  $\sim 40$  to 0 at% in the CoAl(B2)-phase to the boride-phase until the boride is essentially depleted of Al. Conversely, W and B are measured to partition strongly to the boride phase. The composition of the CoAl(B2) phase is Co-36.5Al-2.4W at%, while the composition of the boride phase is Co-38.6W-23.5B at%. Both values, with  $2\sigma$  errors in composition, are summarized in Table 3. The segregation of W at the GB in the 0.05B alloy explains PDZ formation in that as W diffuses from the matrix to GBs to create

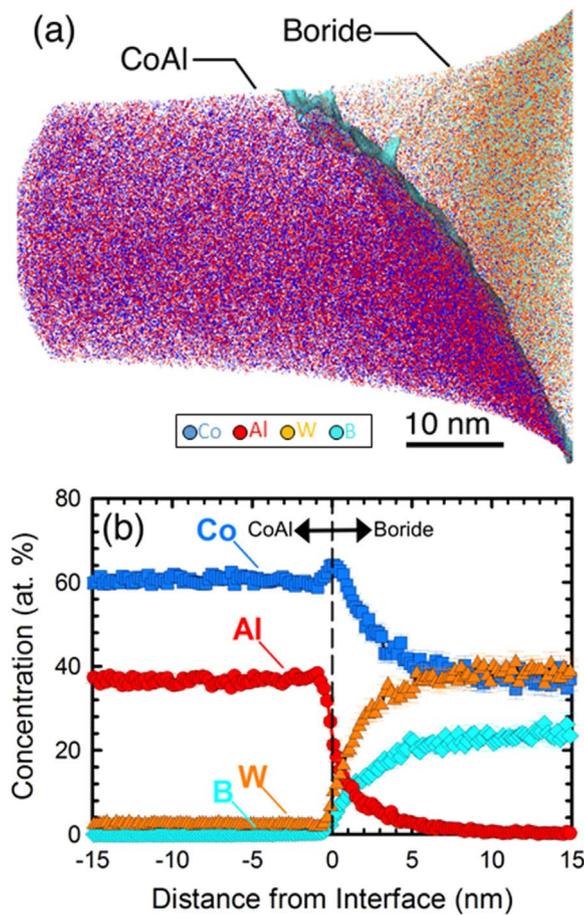

**Fig. 4.** (a) Atom-probe tomographic reconstruction of a CoAl(B2)/boride interface found at a GB in the Co-9.5Al-7.5W-0.05B at% alloy; and (b) corresponding proximity histogram concentration profile.

**Table 3**

The concentration profile at the interface of a boride and CoAl(B2)-phase located at a grain boundary of the Co-9.5Al-7.5W-0.05B alloy as measured employing APT.

Element	Concentration $\pm 2\sigma$ (at%)	
	Boride	B2
Co	37.05 $\pm$ 2.44	60.61 $\pm$ 1.38
Al	<0.01	36.49 $\pm$ 1.41
W	38.62 $\pm$ 2.71	2.40 $\pm$ 0.41
B	23.49 $\pm$ 2.13	<0.01

borides, the regions near GBs become depleted in these elements. Thus, the local composition around the borides shifts toward the  $\gamma$ (f.c.c.)-phase field and the  $\gamma'$ (L1<sub>2</sub>)-precipitates dissolve into the matrix.

### 3.4.2. Grain-boundary segregation of B and Zr in the 0.01B and 0.005B-0.05Zr alloys

One dimensional concentration profiles across GBs of the 0.01B and 0.005B-0.05Zr alloys were measured utilizing an approach similar to that described in the literature [41,42], employing a dual-beam FIB microscope lift-out process with subsequent APT analyses (Fig. 5). The concentration profiles were measured at a 0.2 nm step size from cylindrical region of interest with areas of 475 nm<sup>2</sup> and 600 nm<sup>2</sup> for the 0.01B (Fig. 6a) and 0.005B-0.05Zr (Fig. 6b) alloy, respectively. The B isoconcentration surface is taken to represent a GB, because it is known that B segregates at GBs [28] in Co-base superalloys. Borides were not found at the grain boundaries analyzed with APT implying

that 0.01 at% B is below the solubility limit of B at the grain boundary, in contrast to 0.05 at% B, which was observed to form large grain boundary borides.

The peak B concentration at a GB in 0.01B is  $1.03 \pm 0.11$  at%, which is 100 times greater than the 0.01 B at% bulk concentration. The peak B and Zr concentrations at a GB in 0.005B-0.05Zr are  $0.89 \pm 0.29$  at% B and  $0.99 \pm 0.33$  at% Zr, which are 200 and 20 times greater, respectively, than the bulk concentration. In both alloys, the B concentration is undetectable, within error, in the matrix. This also is true for Zr in the 0.005B-0.05Zr alloy.

GB segregation is quantified by calculating the Gibbsian interfacial excess at a GB,  $\Gamma_i$ , where the subscript  $i$  indicates the segregating atomic species [43]:

$$\Gamma_i = (N_i^{GB} - N_i^0) / A_i; \quad (2)$$

where  $N_i^{GB}$  is the number of atoms  $i$  present at a GB,  $N_i^0$  is the number of  $i$  atoms in the reference state, and  $A_i$  is the area of the interface being sampled [44]. In this case, the reference state is the concentration of the  $\gamma$ (f.c.c.)-matrix phase. The values for  $\Gamma_i$  for Co, Al, W, B, and Zr in the 0.01B and 0.005B-0.05Zr alloys are summarized in Table 3. A negative  $\Gamma_i$  indicates local depletion of a given species at a GB while a positive  $\Gamma_i$  indicates a local excess. In addition to B and Zr, which are expected to segregate at GBs, Co, Al, and W also exhibit segregation or depletion behavior. In 0.01B, Co and Al are depleted at the GB, while W is enriched. The 0.005B-0.05Zr and 0.01B alloys exhibit a similar depletion of Al at their corresponding GBs with values of  $-4.61 \pm 0.54$  and  $-5.38 \pm 0.29$  Al atoms nm<sup>-2</sup> respectively. The GB in the 0.01B alloy exhibits, however, almost no segregation of W and is enriched, rather than depleted, of Co. From the Gibbs adsorption isotherm the change in interfacial Gibbsian free energy,  $G$ , due to segregation is calculated using the integral method formulated by Blum et al. [45]:


$$\Delta G_i = \sum_{j=1}^N -(C_i^m(j) - C_i^0(j)) \Delta x k_b T \ln \left( \frac{C_i^m(j)}{C_i^0(j)} \right) \quad (3)$$

where  $\Delta G_i$  is the change in the interfacial Gibbsian free energy due to segregation,  $j$  is the index of the bins of the concentration profile,  $N$  is the total number of bins,  $\Delta x$  is the bin width associated with the concentration profile,  $k_b$  is Boltzmann's constant,  $T$  is temperature (K),  $C_i^m(j)$  is the local measured concentration of species  $i$ , and  $C_i^0(j)$  is the reference concentration, taken to be the  $\gamma$ (f.c.c.)-matrix concentration of species  $i$  [46]. The  $\Delta G_i$  for each species is given in Table 4. Boron and Zr segregation result in much larger values of  $\Delta G_i$  than do Co, Al, or W. Boron segregation results in a decrease of  $\Delta G_i$  of  $363 \pm 47$  mJ m<sup>-2</sup> in the 0.01B alloy and similarly B plus Zr co-segregation leads to a reduction in  $\Delta G_i$  of  $320 \pm 99$  mJ m<sup>-2</sup> in the 0.005B-0.05Zr alloy.

### 3.5. Grain boundary microstructure after creep at 850 °C

The microstructure of the crept samples was imaged to assist in ascertaining the cause of failure during compressive creep at 850 °C (Fig. 7). The samples were crept to the initial stages of compressive failure in which the strain rate begins transitioning from linear steady-state creep to accelerated deformation. The microstructure of areas at and near the GBs in each of the alloys after creep testing are starkly different from GBs of the alloys prior to creep (Fig. 7). GBs located in the interior of the Co-9.5Al-7.5W alloy (Fig. 7a) were observed to have 0.5–4  $\mu$ m wide PDZs containing the  $\gamma$ (f.c.c.)-phase as well as CoAl(B2)-precipitates, which are not present in the untested aged alloy, and large coarsened  $\gamma'$ (L1<sub>2</sub>)-precipitates. The stress-time history varies with each sample, so the resulting microstructures are not directly comparable.

Differences in GB microstructure were also observed for the 0.05B alloy. The semi-continuous GB borides present prior to creep testing (Fig. 1b) are no longer present after creep (Fig. 7b). The regions around the GBs now consist primarily of a  $\gamma$ (f.c.c.)-phase PDZ, where the borides and other minor phases are irregularly dispersed throughout

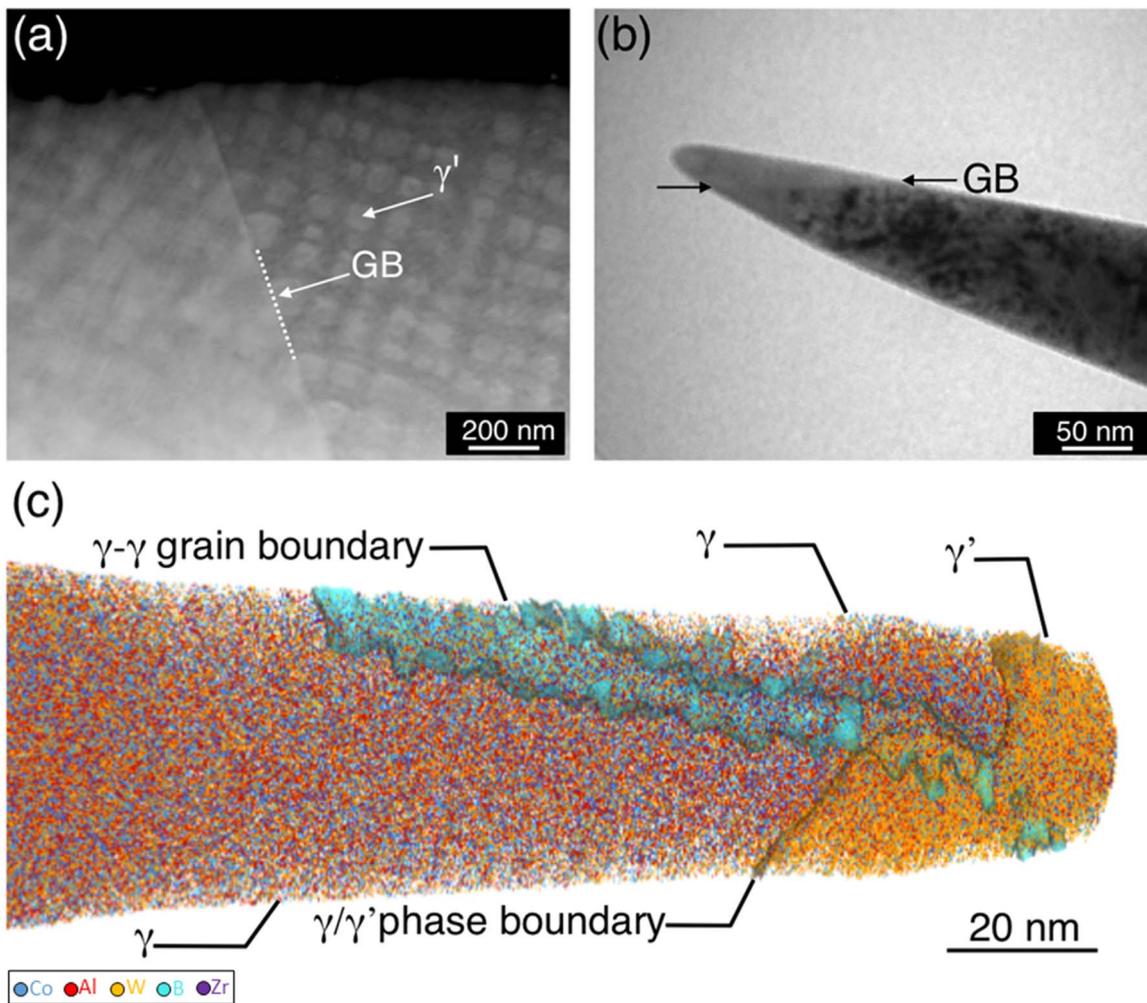

**Fig. 5.** (a) STEM image of a GB in the Co-9.5Al-7.5W-0.005B-0.05Zr at% alloy. (b) Atom-probe tomographic nanotip fabricated employing the FIB lift-out technique of the same GB. (c) Atom-probe tomographic 3D reconstruction of the nanotip displayed in (b). A boron (cyan) isoconcentration surface is used to delineate the two grains. A tungsten (orange) isoconcentration surface is used to designate a  $\gamma'$ (L1<sub>2</sub>)-precipitate at the end of the nanotip.

the PDZ. The  $\gamma'$ (L1<sub>2</sub>)-precipitates adjacent to the PDZ have not coarsened in contrast to the other alloys. The occasional Co<sub>3</sub>W(DO<sub>19</sub>)- and CoAl(B2)-precipitates were observed within the PDZ, where the average compositions were measured from 7 to 10 precipitates with EDS to be Co-39.1W and Co-35.9Al-3.0W at%, respectively.

The regions around GBs in the crept 0.01B alloy (Fig. 7c) are comparable to those observed for the crept Co-9.5Al-7.5W alloy. These regions contain elongated portions of coarsened  $\gamma'$ (L1<sub>2</sub>)-precipitates as well as regions devoid of precipitates, leading to wide PDZs between adjacent grains. GB precipitation was not observed in the aged 0.01B alloy; CoAl(B2)-precipitates and W-rich borides were, however, found in regions with coarsened  $\gamma'$ (L1<sub>2</sub>)-precipitates in the crept alloy.

The Zr containing alloys also exhibit changes in microstructure around GBs after creep. Compared to all alloys, the 0.05Zr alloy (Fig. 7d) exhibits the most changes; as demonstrated in Fig. 7d; many Co<sub>3</sub>W(DO<sub>19</sub>), CoAl(B2) and coarsened  $\gamma'$ (L1<sub>2</sub>)-precipitates decorate the region near the GBs, in addition there are pockets of precipitate free  $\gamma$ (f.c.c.)-regions. For the crept 0.005B-0.05Zr alloy (Fig. 7e), the GBs contain primarily coarsened  $\gamma'$ (L1<sub>2</sub>)-precipitates without additional minor phases, with the exception of one instance of a Zr-rich phase observed by a wide area survey of the GBs.

## 4. Discussion

### 4.1. Ambient temperature compressive properties

The 0.05B alloy contains GB borides with PDZs on either side of the GB. PDZs have been shown to reduce strongly the yield stress in Ni-base superalloys, e.g., by 10–25% [22]. Being precipitate free, the PDZ serves as an area where dislocations can be created and glide more readily than in the bulk of the alloy, and where  $\gamma'$ (L1<sub>2</sub>)-precipitates are present to inhibit the migration of dislocations. The Co-9.5Al-7.5W, 0.01B, 0.05Zr, and 0.005B-0.05Zr alloys have similar yield stresses indicating that B and Zr have no effect on the room temperature yield strength when GB precipitation is absent.

### 4.2. Creep at 850 °C

The creep results (Fig. 3) demonstrate that GB segregants range from having no effect to having an appreciable improvement of the creep behavior of Co-base superalloys. The alloy containing 0.05B exhibited the strongest increase in creep strength in these alloys, which is attributed to the formation of GB borides. The 0.01B- and 0.05Zr-alloys, in contrast, show no improvement, which differs from Ni-base alloys, where the presence of 0.005–0.1 at% B, at a level insufficient for boride formation, is adequate for strengthening GBs between 650 and 980 °C at stresses between 35 and 550 MPa [23,25,32].

GB borides increase creep strength in similar Co-9Al-9W-X super-

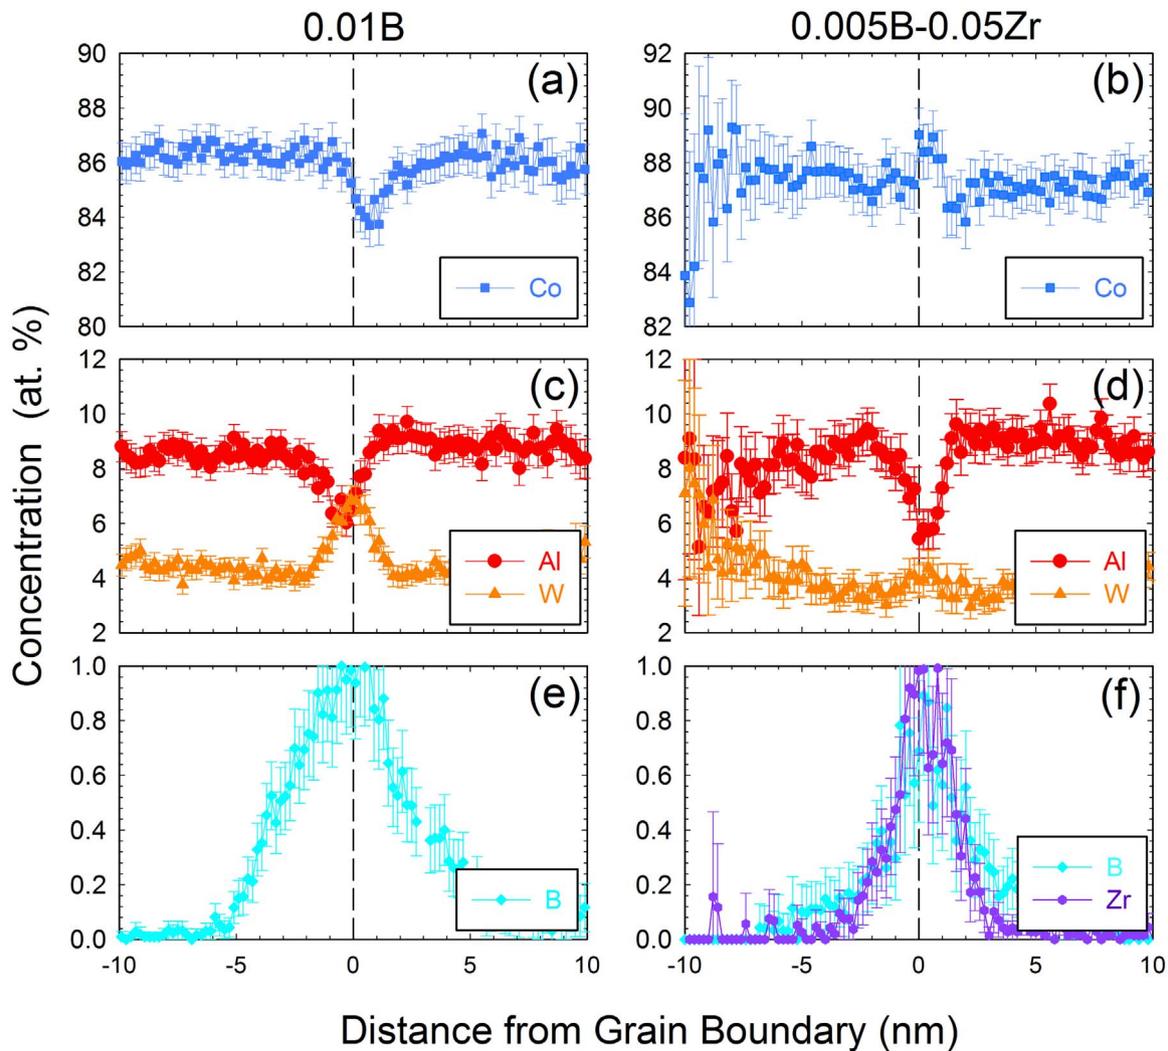


Fig. 6. Plots of the concentration profiles measured with APT along a  $\gamma$ (f.c.c.)-grain boundary in the Co-9.5Al-7.5W-0.01B (left) and Co-9.5Al-7.5W-0.005B-0.05Zr (right) alloy.

alloys [17,20]. To date, a description of the cause of the dramatic increase of creep strength due to the presence of GB borides has been insufficiently explained. Increased GB strength and cohesion is often cited as the reason for increased creep strength, however if GB strengthening is the only mechanism that borides contribute to, the boride free alloys should creep via GB sliding as indicated by a creep stress exponent of  $n=2$ . Furthermore, the large grain size in these alloys would generally not be favorable to diffusional creep process (i.e. Coble and Nabarro-Herring Creep). The stress exponents of boride free alloys presented herein are between 5.4 and 9.9, indicating creep by dislocation climb and glide. A possible explanation may be that the borides serve a dual strengthening role. The presence of borides increases creep life by improving GB cohesion and improves creep strength by stabilizing GBs, thereby protecting the GBs from precipitation of deleterious phases. Postmortem SEM analyses of GBs, Fig. 7, shows that the microstructure of regions near GBs contains large PDZs often


with  $\text{Co}_3\text{W}(\text{D0}_{19})$ ,  $\text{CoAl}(\text{B2})$ , and coarsened  $\gamma'(\text{L1}_2)$ -precipitates. These regions likely serve as areas of easy dislocation glide, thereby lowering the creep strength. In alloys with GB borides, regions near GBs degrade at higher stresses than GBs in boride-free alloys.

The addition of 0.01B and 0.05Zr, individually, does not have a significant impact on the creep strength of the Co-9.5Al-7.5W-X alloy; the simultaneous addition of 0.005B and 0.05Zr improves creep resistance, indicating a synergistic effect. The exact mechanism, which does not rely on borides, is unknown, and future research is required to study GBs correlatively utilizing TEM and APT. One possible explanation is that, because combined B and Zr GB segregation appears to reduce W segregation to GBs (Fig. 6) deleterious brittle phases, such as  $\text{Co}_3\text{W}(\text{D0}_{19})$ , are unable to form thereby making the GBs in B-Zr-containing alloys more stable.

Table 4

Gibbsian interfacial excess ( $\Gamma_i$ ) and the resulting reduction in the Gibbsian interfacial Gibbs free energy ( $\Delta G$ ) of a grain boundary in the Co-9.5-7.5-0.01B and Co-9.5-7.5-0.005B-0.05Zr alloys, as calculated from the concentration profiles of solute atoms across the grain boundary. The  $2\sigma$  errors are given in parenthesis.

Alloy	Interfacial Excess $\Gamma_i$ ( atoms $\text{nm}^{-2}$ )					$\Delta G$ ( $\text{mJ m}^{-2}$ )				
	Co	Al	W	B	Zr	Co	Al	W	B	Zr
0.01B	-3.70 (0.02)	-5.38 (0.29)	4.32 (0.23)	5.57 (1.04)	-	2.30 (0.02)	31.61 (1.77)	40.32 (2.32)	362.54 (47.39)	-
0.005B-0.05Zr	1.22 (0.01)	-4.61 (0.54)	0.48 (0.07)	2.88 (0.81)	2.40 (0.84)	0.55 (0.01)	25.91 (3.15)	2.69 (0.40)	168.26 (77.68)	152.78 (61.89)

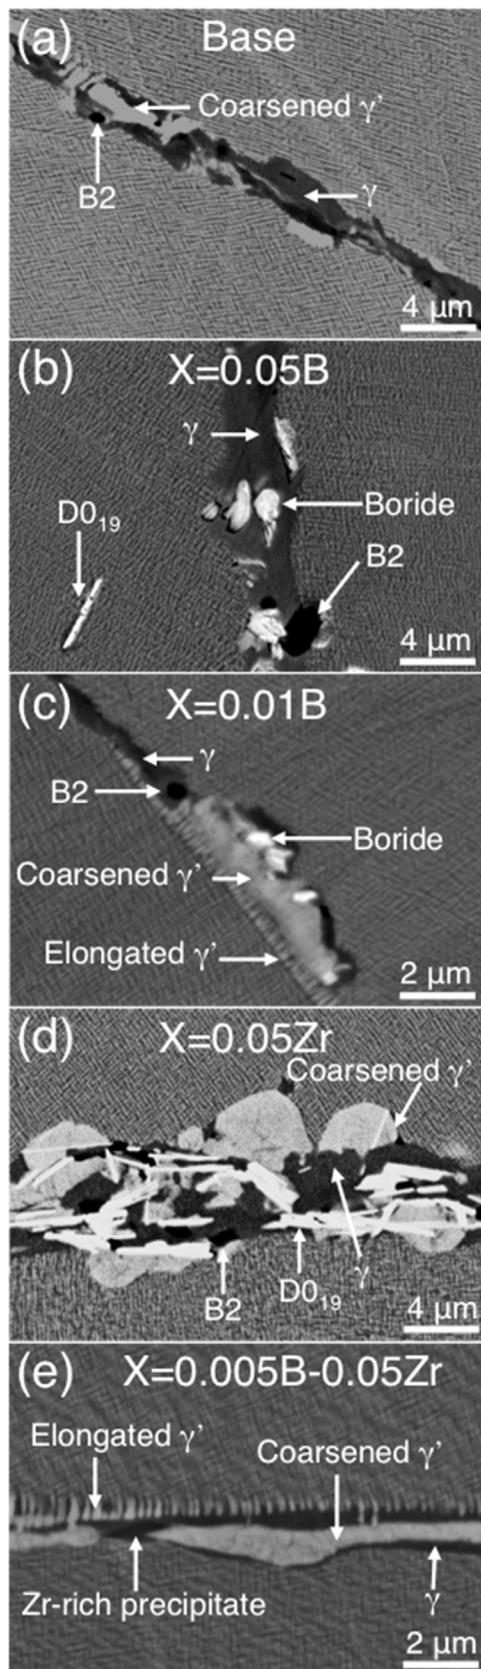

**Fig. 7.** Backscattered electron SEM micrographs showing different forms of grain boundary precipitation after creep at 850 °C in: (a) Co-9.5Al-7.5W ( $t=476$  h,  $\sigma=105$ – $235$  MPa); (b) Co-9.5Al-7.5W-0.05B ( $t=25$  h,  $\sigma=309$ – $398$  MPa); (c) Co-9.5Al-7.5W-0.01B ( $t=121$  h,  $\sigma=176$  MPa); (d) Co-9.5Al-7.5W-0.05Zr ( $t=248$  h,  $\sigma=127$ – $184$  MPa); and (e) Co-9.5Al-7.5W-0.005B-0.05Zr ( $t=73$  h,  $\sigma=220$ – $308$  MPa).

**Table 5**

Enthalpies of formation ( $\Delta H_f$ ) of different borides commonly formed with Al, Co, W and Zr.

Boride	$\Delta H_f$ kJ mol <sup>-1</sup>
AlB <sub>2</sub> [47,48]	-8 to -29
Co <sub>2</sub> B [49]	-52 to -69
CoB [49]	-62 to -75
W <sub>2</sub> B [50]	-84 to -117
W <sub>2</sub> B <sub>5</sub> [50]	-105 to -188
WB [50]	-50 to -92
ZrB <sub>2</sub> [50,51]	-248 to -323

#### 4.3. Implications of Zr segregation at grain boundaries in the 0.005B-0.05Zr alloy

Segregation of B and Zr at GBs strengthens them in Ni-base superalloys [23,25,32], but GB segregants in the Co-base superalloys have not yet been studied in detail. Zirconium additions combined with B have a positive influence on the creep properties of polycrystalline Co-Al-W alloys (Fig. 3). Segregation of B and Zr at GBs in the 0.005B-0.05Zr alloy implies that zirconium borides, rather than tungsten borides, may form at GBs once they have achieved the maximum concentrations permitted by the Gibbs adsorption isotherm. This would decrease, and possibly even eliminate, W segregation at the GBs, hence eliminating the PDZs that form in alloys containing only B for GB strengthening. Enthalpies of formation [47–51] for different Co, Al, W, and Zr borides are compiled in Table 5. ZrB<sub>2</sub> has the most negative enthalpy of formation of any of the other compounds, followed by the W-, Co-, and Al-borides, which is consistent with the strong Zr-B bonding. Therefore, it is possible that increasing the Zr and B concentrations beyond those studied herein could further strengthen the GBs and improve creep properties through the formation of Zr-rich borides, while limiting PDZ width that occurs due to the formation of W-rich borides.

#### 4.4. Grain boundary failure

In all events of failure in this research the cause was observed to be intergranular fracture, which emphasizes the need for GB strengtheners in polycrystalline Co-base superalloys. SEM of the post-creep microstructures (Fig. 7) presents different examples of GB microstructures, which typically includes heavily coarsened  $\gamma'$ (L1<sub>2</sub>)-precipitates and less coarse Co<sub>3</sub>W(D0<sub>19</sub>) and CoAl(B2) precipitates, which have a much different morphology than GBs in the aged condition (Fig. 1). Discerning whether precipitation at the GBs is the result or the cause of failure is not obvious. In the former case, other systems exhibit GB precipitation caused by GB sliding and fracture [52]. In the latter case, there are many articles challenging the stability of the  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) phase field in the Co-Al-W system [53–55]. In a situation where the  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>)-phase field is metastable or barely stable, GBs in the presence of stress may serve as heterogeneous nucleation regions for formation of the stable, but undesirable Co<sub>3</sub>W(D0<sub>19</sub>) and CoAl(B2) phases.

## 5. Summary

One ternary Co-9.5Al-7.5W at%, three quaternary Co-9.5Al-7.5W-X at% (where X=0.05B, 0.01B, 0.05Zr), and one quinary Co-Al-W-X at% (with X=0.005B+0.05Zr) alloys were cast and aged to obtain a  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) microstructure. The GB segregation behavior and mechanical properties of B and Zr containing Co-base superalloys were characterized via 3-D atom-probe tomographic analyses, compression testing, and high-temperature compression creep. The following conclusions are reached:

- Boron and Zr were shown to segregate strongly at GBs in the Co-9.5Al-7.5W-0.01B at% and Co-9.5Al-7.5W-0.005B-0.05Zr at% alloys. Simultaneous addition of 0.005B and 0.05Zr to Co-9.5Al-7.5W at% improved creep strength over the baseline ternary alloy without forming GB borides.
- Boron segregation at GBs leads to large W-rich borides in Co-9.5Al-7.5W-0.05B at%, but not in Co-9.5Al-7.5W-0.01B at% alloy, suggesting that the amount of B at grain boundaries in the 0.01B sample are below the GB solubility limit. Tungsten diffuses from the matrix to the GBs to form the borides, leaving the matrix W-deficient, thus moving the local composition from the  $\gamma$ (f.c.c.) plus  $\gamma'$ (L1<sub>2</sub>) to the  $\gamma$ (f.c.c.) phase-field and creating a  $\gamma'$ (L1<sub>2</sub>)-precipitate denuded zone (PDZ) near the GBs.
- GB borides have a strong effect on the creep strength by strengthening them as exhibited by a pronounced decrease in the minimum steady-state strain rate by two orders of magnitude for a given stress when compared to Co-9.5Al-7.5W at%.
- The PDZ acts a soft region for easy dislocation movement, with the effect that the yield strength at room temperature decreases from 598 MPa in the base Co-Al-W to 564 MPa alloy in the Co-9.5Al-7.5W-0.05B at% alloy containing grain-boundary borides.
- A GB boride in the Co-9.5Al-7.5W-0.05B at% alloy was measured for the first time and was found to have a composition of Co-38.62W-23.49B at%, with nearly equal amounts of Co and W, and no Al.
- Regions near the GBs of crept alloys exhibit a large amount of precipitation, primarily comprised of Co<sub>3</sub>W(D0<sub>19</sub>) (Co-39.1W at%), CoAl(B2) (Co-36.5Al-2.4W at%), and coarsened  $\gamma'$ (L1<sub>2</sub>)-precipitates, plus precipitate depleted zones not observed in uncrept alloys.

## Acknowledgments

This research was supported by the US Department of Energy, Office of Basic Energy Sciences (Dr. John Vetrano, grant monitor) through grant DE-FG02-98ER45721. P.J.B. received partial support from the NASA Aeronautics Scholarship Program (Grant No. NNX14AF45H) and Fixed Wing project. APT measurements were performed at the Northwestern University Center for Atom-Probe Tomography (NUCAPT). The APT system was purchased and upgraded with funding from NSF-MRI (DMR-0420532) and ONR-DURIP (N00014-0400798, N00014-0610539 and N00014-0910781) grants. NUCAPT is a shared facility of the Materials Research Center of NU, supported by the National Science Foundation MRSEC Program (DMR-1121262). The authors also gratefully acknowledge the Initiative for Sustainability and Energy at Northwestern (ISEN) for grants to upgrade the capabilities of NUCAPT. This work made use of Northwestern's Materials Research Center's core facilities funded by the NSF MRSEC program (DMR-112162). TEM research was performed at the Northwestern University Atomic and Nanoscale Characterization Experimental (NUANCE) Center. The authors would like to thank research associate professor D. Isheim for managing NUCAPT, Dr. S.-I. Baik (Northwestern University) for assistance with transmission electron microscopy, Drs. Dave Ellis and Cheryl Bowman (NASA Glenn Research) for assistance with creep experiments, Mr. Grant Feichter and Jesse Bierer for arc melting and heat treating (NASA Glenn Research), and Dr. Tim Gabb (NASA Glenn Research) for helpful discussions.

## References

- [1] R.C. Reed, *The Superalloys*, Cambridge University Press, New York, 2006.
- [2] C.T. Sims, N.S. Stoloff, W.C. Hagel, *Superalloys II*, John Wiley & Sons Inc, New York, 1987.
- [3] P. Caron, T. Khan, Evolution of Ni-based superalloys for single crystal gas turbine blade applications, *Aerosp. Sci. Technol.* 3 (1999) 513–523.
- [4] T.M. Pollock, A.S. Argon, Creep resistance of CMSX-3 nickel base superalloy single crystals, *Acta Metall.* 40 (1992) 1–30.
- [5] M. Durand-Charre, *The Microstructure of Superalloys*, Gordon and Breach Science Publishers, Amsterdam, 1997.
- [6] Haynes International, Haynes 188 Alloy, Standard Products by Brand or Alloy Designation.
- [7] J. Sato, T. Omori, K. Oikawa, I. Ohnuma, R. Kainuma, K. Ishida, Cobalt-base high-temperature alloys, *Science* 312 (2006) 90–91.
- [8] F. Pyczak, A. Bauer, M. Göken, U. Lorenz, S. Neumeier, M. Oehring, J. Paul, N. Schell, A. Schreyer, A. Stark, F. Symanzik, The Effect of tungsten content on the properties of L12-hardened Co–Al–W alloys, *J. Alloy. Compd.* 632 (2015) 110–115.
- [9] H.-Y. Yan, V.A. Vorontsov, D. Dye, Alloying effects in polycrystalline  $\gamma'$  strengthened Co–Al–W base alloys, *Intermetallics* 48 (2014) 44–53.
- [10] Y.M. Eggeler, M.S. Titus, A. Suzuki, T.M. Pollock, Creep deformation-induced antiphase boundaries in L12-containing single-crystal cobalt-base superalloys, *Acta Mater.* 77 (2014) 352–359.
- [11] M.S. Titus, A. Suzuki, T.M. Pollock, Creep and directional coarsening in single crystals of new  $\gamma'$ -cobalt-base alloys, *Scr. Mater.* 66 (2012) 574–577.
- [12] M.S. Titus, A. Suzuki, T.M. Pollock, High temperature creep of new L12-containing cobalt-base superalloys, *Superalloys 12* (2012) 823–831.
- [13] A. Suzuki, T.M. Pollock, High-temperature strength and deformation of  $\gamma/\gamma'$  two-phase Co–Al–W-base alloys, *Acta Mater.* 56 (2008) 1288–1297.
- [14] A. Suzuki, G.C. Denolf, T.M. Pollock, Flow stress anomalies in  $\gamma/\gamma'$  two-phase Co–Al–W-base alloys, *Scr. Mater.* 56 (2007) 385–388.
- [15] F. Xue, H.J. Zhou, Q.Y. Shi, X.H. Chen, H. Chang, M.L. Wang, Q. Feng, Creep behavior in a  $\gamma'$  strengthened Co–Al–W–Ta–Ti single-crystal alloy at 1000 °C, *Scr. Mater.* 97 (2015) 37–40.
- [16] A. Bauer, S. Neumeier, F. Pyczak, M. Göken, Microstructure and creep strength of different  $\gamma/\gamma'$ -strengthened Co-base superalloy variants, *Scr. Mater.* 63 (2010) 1197–1200.
- [17] A. Bauer, S. Neumeier, F. Pyczak, R.F. Singer, M. Göken, Creep properties of different  $\gamma'$ -strengthened Co-base superalloys, *Mater. Sci. Eng. A* 550 (2012) 333–341.
- [18] I. Povstugar, P.-P. Choi, S. Neumeier, A. Bauer, C.H. Zenk, M. Göken, D. Raabe, Elemental partitioning and mechanical properties of Ti- and Ta-containing Co–Al–W-base superalloys studied by atom probe tomography and nanoindentation, *Acta Mater.* 78 (2014) 78–85.
- [19] K. Tanaka, M. Ooshima, N. Tsuno, A. Sato, H. Inui, Creep deformation of single crystals of new Co–Al–W-based alloys with fcc/L12 two-phase microstructures, *Philos. Mag.* 92 (2012) 4011–4027.
- [20] A. Bauer, S. Neumeier, F. Pyczak, M. Göken, Creep strength and microstructure of polycrystalline  $\gamma'$  – strengthened cobalt-base superalloys, *Superalloys 12* (2012) 695–703.
- [21] K. Shinagawa, T. Omori, K. Oikawa, R. Kainuma, K. Ishida, Ductility enhancement by boron addition in Co–Al–W high-temperature alloys, *Scr. Mater.* 61 (2009) 612–615.
- [22] T. Krol, D. Baither, E. Nembach, The formation of precipitate free zones along grain boundaries in a superalloy and the ensuing effects on its plastic deformation, *Acta Mater.* 52 (2004) 2095–2108.
- [23] T.J. Garosshen, T.D. Tillman, G.P. McCarthy, Effects of B, C, and Zr on the structure and properties of a P/M nickel base superalloy, *Metall. Trans. A* 18A (1987) 69–77.
- [24] T.H. Chuang, The mutual effects of boron, zirconium, and aluminum on grain boundary segregation in Ni3Al intermetallic compounds, *Mater. Sci. Eng. A* 141 (1991) 169–178.
- [25] E.S. Huron, K.R. Bain, D.P. Mourer, J.J. Schirra, P.L. Reynolds, E.E. Montero, The Influence of grain boundary elements on properties and microstructures of P/M nickel base superalloys, *Superalloys* (2004) 73–81.
- [26] L. Klein, B. von Bartenwerffer, M.S. Killian, P. Schmuki, S. Virtanen, The effect of grain boundaries on high temperature oxidation of new  $\gamma'$ -strengthened Co–Al–W–B superalloys, *Corros. Sci.* 79 (2014) 29–33.
- [27] L. Klein, S. Virtanen, Corrosion properties of novel  $\gamma'$ -strengthened Co-base superalloys, *Corros. Sci.* 66 (2013) 233–241.
- [28] L. Klein, Y. Shen, M.S. Killian, S. Virtanen, Effect of B and Cr on the high temperature oxidation behaviour of novel  $\gamma/\gamma'$ -strengthened Co-base superalloys, *Corros. Sci.* 53 (2011) 2713–2720.
- [29] L. Klein, A. Bauer, S. Neumeier, M. Göken, S. Virtanen, High temperature oxidation of  $\gamma/\gamma'$ -strengthened Co-base superalloys, *Corros. Sci.* 53 (2011) 2027–2034.
- [30] W.Z. Wang, H.U. Hong, I.S. Kim, B.G. Choi, H.W. Jeong, M.Y. Kim, C.Y. Jo, Influence of  $\gamma'$  and grain boundary carbide on tensile fracture behaviors of nimonic 263, *Mater. Sci. Eng. A* 523 (2009) 242–245.
- [31] F.T. Furillo, J.M. Davidson, J.K. Tien, L.A. Jackman, The effects of grain boundary carbides on the creep and back stress of a nickel-base superalloy, *Mater. Sci. Eng.* 39 (1979) 267–273.
- [32] S. Floreen, J.M. Davidson, The Effects of B and Zr on the creep and fatigue crack growth behavior of a Ni-base superalloy, *Metall. Trans. A* 14A (1983) 895–901.
- [33] D.N. Seidman, K. Stiller, An atom-probe tomography primer, *Mater. Res. Bull.* 34 (2009) 717–721.
- [34] D.N. Seidman, Three-dimensional atom-probe tomography: advances and applications, *Annu. Rev. Mater. Sci.* 37 (2007) 127–158.
- [35] C.K. Sudbrack, R.D. Noebe, D.N. Seidman, Direct observations of nucleation in a nondilute multicomponent alloy, *Phys. Rev. B* 73 (2006) 1–4.
- [36] J.C. Russ, R.T. Dehoff, *Practical Stereology*, 2 ed., Springer, New York, New York, 1986.
- [37] B.W. Krakauer, J.G. Hu, S.-M. Kuo, R.L. Mallick, A. Seki, D.N. Seidman, J.P. Baker, R. Loyd, A system for systematically preparing atom-probe field-ion microscope specimens for the study of internal interfaces, *Rev. Sci. Instrum.* 61 (1990) 3390–3398.

- [38] B.W. Krakauer, D. Seidman, Systematic procedures for atom-probe field-ion microscopy studies of grain boundary segregation, *Rev. Sci. Instrum.* 63 (1992) 4071–4079.
- [39] F. Danoix, G. Granicher, A. Bostel, D. Blavette, Standard deviations of composition measurements in atom probe analyses—Part II: 3D atom probe, *Ultramicroscopy* 107 (2007) 739–743.
- [40] O.C. Hellman, J.A. Vandembroucke, J. Rusing, D. Isheim, D.N. Seidman, Analysis of three-dimensional atom-probe data by the proximity histogram, *Microsc. Microanal.* 6 (2000) 437–444.
- [41] H. Li, S. Xia, W. Liu, T. Liu, B. Zhou, Atomic scale study of grain boundary segregation before carbide nucleation in Ni–Cr–Fe alloys, *J. Nucl. Mater.* 439 (2013) 57–64.
- [42] S.-I. Baik, M.J. Olszta, S.M. Bruegger, D.N. Seidman, Grain-boundary structure and segregation behavior in a nickel-base stainless alloy, *Scr. Mater.* 66 (2012) 809–812.
- [43] J.W. Cahn, W.C. Johnson, J.M. Blakely (Eds.), *Thermodynamics of Solid and Fluid Surfaces*, ASM, Metals Park, Ohio, 1978, pp. 3–23.
- [44] O.C. Hellman, J. Rusing, J.T. Sebastian, D.N. Seidman, Atom-by-atom chemistry of internal interfaces: simulations and experiments, *Mater. Sci. Eng. C* 15 (2001) 13–15.
- [45] I.D. Blum, S.-I. Baik, M.G. Kanatzidis, D.N. Seidman, An Integral Method for the Calculation of the Reduction in Interfacial Free energy due to interfacial segregation, January 2016 (Submitted for publication).
- [46] A. Biswas, D.J. Siegel, C. Wolverton, D.N. Seidman, Precipitates in Al–Cu alloys revisited: atom-probe tomographic experiments and first-principles calculations of compositional evolution and interfacial segregation, *Acta Mater.* 59 (2011) 6187–6204.
- [47] M.J. van Setten, M. Fichtner, On the enthalpy of formation of aluminum diboride, AlB<sub>2</sub>, *J. Alloy. Compd.* 477 (2009) L11–L12.
- [48] D. Mirković, J. Gröbner, R. Schmid-Fetzer, O. Fabrichnaya, H.L. Lukas, Experimental study and thermodynamic re-assessment of the Al–B system, *J. Alloy. Compd.* 384 (2004) 168–174.
- [49] S. Sato, O.J. Kleppa, Enthalpies of formation of borides of iron, cobalt, and nickel by solution calorimetry in liquid copper, *Metall. Trans. B* 13 (1982) 251–257.
- [50] E.S. Domalski, G.T. Armstrong, USAF (Ed.) *Heats of Formation of Metallic Borides by Fluorine Bomb Calorimetry*, National Bureau of Standards, Washington D.C., 1964.
- [51] E.J. Huber, E.L. Head, C.E. Holley, The heats of formation of zirconium diboride and dioxide, *J. Phys. Chem.* 68 (1964) 3040–3042.
- [52] J. Wadsworth, O. Ruano, O. Sherby, Denuded zones, diffusional creep, and grain boundary sliding, *Metall. Mater. Trans. A* 33 (2002) 219–229.
- [53] S. Kobayashi, Y. Tsukamoto, T. Takasugi, H. Chinen, T. Omori, K. Ishida, S. Zaefferer, Determination of phase equilibria in the Co-rich Co–Al–W ternary system with a diffusion-couple technique, *Intermetallics* 17 (2009) 1085–1089.
- [54] Y. Tsukamoto, S. Kobayashi, T. Takasugi, The stability of  $\gamma'$ -Co<sub>3</sub>(Al,W) phase in Co–Al–W ternary system, *Mater. Sci. Forum* 654–656 (2010) 448–451.
- [55] S. Kobayashi, Y. Tsukamoto, T. Takasugi, The effects of alloying elements (Ta, Hf) on the thermodynamic stability of  $\gamma'$ -Co<sub>3</sub>(Al,W) phase, *Intermetallics* 31 (2012) 94–98.